

AD 609001

REMOVED FROM THE RE-
TRIBUT-
DEPARTMENT OF

Rock Island Arsenal Laboratory



COPY	2	OF	3	1
HARD COPY	\$.075			
MICROFICHE	\$.050			

DDC 23
RECEIVED
DEC 21 1964
DOCIRA C

TECHNICAL REPORT

ELASTOMERIC INSULATION FOR SOLID PROPELLANT
ROCKET MOTORS

By

D. H. Sale

ARCHIVE COPY

Department of the Army Project No. 1C0-24401-A110

AMC Code No. 5025.11.84203

Report No. 64-3158

Copy No.

IEL No. 1-9-100-2

Date 27 October 1964

DISTRIBUTED BY THE
OFFICE OF TECHNICAL SERVICES
U. S. DEPARTMENT OF COMMERCE
WASHINGTON 25, D. C.

THIS REPORT MAY BE DESTROYED WHEN
NO LONGER REQUIRED FOR REFERENCE

The findings in this report are not to be construed
as an official Department of the Army position.


"Copies Available at Office of Technical Services \$.75".

Report No. 64-3158

Copy No. _____

**ELASTOMERIC INSULATION FOR SOLID PROPELLANT
ROCKET MOTORS**

By



D. H. Sale

Approved by:



A. C. HANSON
Laboratory Director

27 October 1964

DA Project No. 1C0-244C1-A110

AMC Code No. 5025 11.84203

Rock Island Arsenal
Rock Island, Illinois

DDC Availability Notice:

Qualified requesters may obtain
copies of this report from DDC.

ABSTRACT

The development of flexible, elastomeric-based, solid propellant rocket motor case insulation is discussed. The effect on insulation properties of type of asbestos, of liquid versus solid elastomers and of methods of dispersing fibrous compounding ingredients, are reported.

Oxyacetylene torch and static motor firing test data for some of the better insulation materials developed, as well as for some commercial materials, are presented. The torch test, the principle screening tool used in this study, conforms to the test currently being standardized by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20.

A material with 40 percent elongation, 1.34 gm/cc density, performance index of 95 cm²sec/gm and erosion rate of 2.0 mils/sec was the most promising insulation developed. The material is a 55/45 butadiene/acrylonitrile compound containing phenol furfural resin, asbestos and oxyazoline wetting agent. It has been satisfactorily bonded to aluminum and to steel by conventional bonding agent. The thermal properties of this vulcanizate are not affected by oven aging for one week at 70°C.

RECOMMENDATIONS

It is recommended that this project be discontinued. It is believed that the insulation materials developed during the course of this investigation represent an advancement in the state of the art and that further investigations under the approaches outlined in this and earlier work would result in only marginal improvements.

It is recommended that the oxyacetylene torch test equipment be retained in a usable condition, in order that promising new commercial insulation materials might be evaluated and that cooperative work to further improve this screening test might be conducted, if necessary

ELASTOMERIC INSULATION FOR SOLID PROPELLANT
ROCKET MOTORS

CONTENTS

	<u>Page No.</u>
Object	1
Introduction	1
Procedure	2
Results and Discussion	4
Literature References	14
Appendix I	16
Appendix II	17
Distribution	18

ELASTOMERIC INSULATION FOR SOLID PROPELLANT ROCKET MOTORS

OBJECT

To develop improved, flexible, thermal case insulation for solid propellant rocket motors.

INTRODUCTION

The need for flexible rocket motor case insulation has been well established. (1-7) Elastomers have played an important role in meeting this need, as evidenced by the many types of elastomeric-based insulations which have been developed for use in solid propellant missiles. The wide spectrum of commercially available insulation ranges from lightly filled rubbers with excellent flexibility but minimal ablation resistance, to highly loaded compounds with little flexibility but outstanding resistance to the high temperatures and erosive gases found within rocket motors.

Present day elastomeric insulations are not considered adequate for future needs, especially needs related to the use of end burning grains. It is anticipated that longer burning times at higher temperatures will necessitate more thermally resistant insulations and that higher internal pressures will require higher degrees of flexibility. A continuing need exists for lighter weight materials.

It appears that maximum flexibility and resistance to the environments within rocket motors are mutually exclusive properties, insofar as rubber-based insulations are concerned, since improvements in one property are attainable only at the expense of the other. Earlier work at this Arsenal, (8,9) as well as more recent studies, has led to the development of rubber-based insulations having a compromise in these two properties, namely, the highest degree of ablative resistance which could be attained together with flexibility which, when measured in terms of elongation, amounts to 20 to 50 percent. Results of these studies have led to the following conclusions:

1. By far the most effective filler combination for imparting ablation resistance to rubber vulcanizates is a combination of a phenolic resin and long fiber asbestos.

2. This filler combination is most effective in a high nitrile content, butadiene/acrylonitrile elastomer. Of the more than 400 combinations of elastomers, fillers

and other compounding ingredients tested, none has led to a material having a better compromise between flexibility and ablation resistance than that exhibited by the nitrile-phenolic resin-asbestos fiber system.

3. The degree of ablation resistance of this, or any other asbestos-containing rubber compound, is directly related to the fiber length of the asbestos in the finished product.

These findings largely influenced the direction of effort described in this report. Minimum effort has been devoted to seeking more effective combinations of rubber and fillers. Major emphasis has been placed on developing means for incorporating long fiber asbestos into rubber-resin matrices without significantly reducing fiber length.


PROCEDURE

Insulation resistance was determined with an oxy-acetylene torch test (Figure 1) using the conditions cited in Table I. The equipment and procedures duplicate those of the test currently in the final stages of standardization by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20.

The effectiveness of candidate insulation materials was measured by two test criteria; (1) the temperature rise on the back side of the specimen while the front side was exposed to the oxyacetylene torch flame and (2) the time required for the flame to burn through the specimen. These criteria are reported as performance indices and erosion rates, respectively. The index, referred to as P₂₀₀, is computed by dividing the time (seconds) required for the specimen back side to reach 200°C. by the original specimen thickness (centimeters) and by the specimen specific gravity. The erosion rate, E, is computed by dividing the original specimen thickness (mils) by the burn through time. It should be noted that high values of P₂₀₀ and low values for E are indicative of good insulation properties. Unless otherwise noted, the performance indices and erosion rates reported are the average of four test results

Rock Island Arsenal Laboratory has been an active member of the aforementioned ASTM Test Group. The torch test facility at this Laboratory was among those utilized in a recent round robin. The round robin results showed an average variance among laboratories of less than ±5% for each of the two test criteria. The Rock Island Arsenal test facility produced results well within this variance.

FIGURE 1

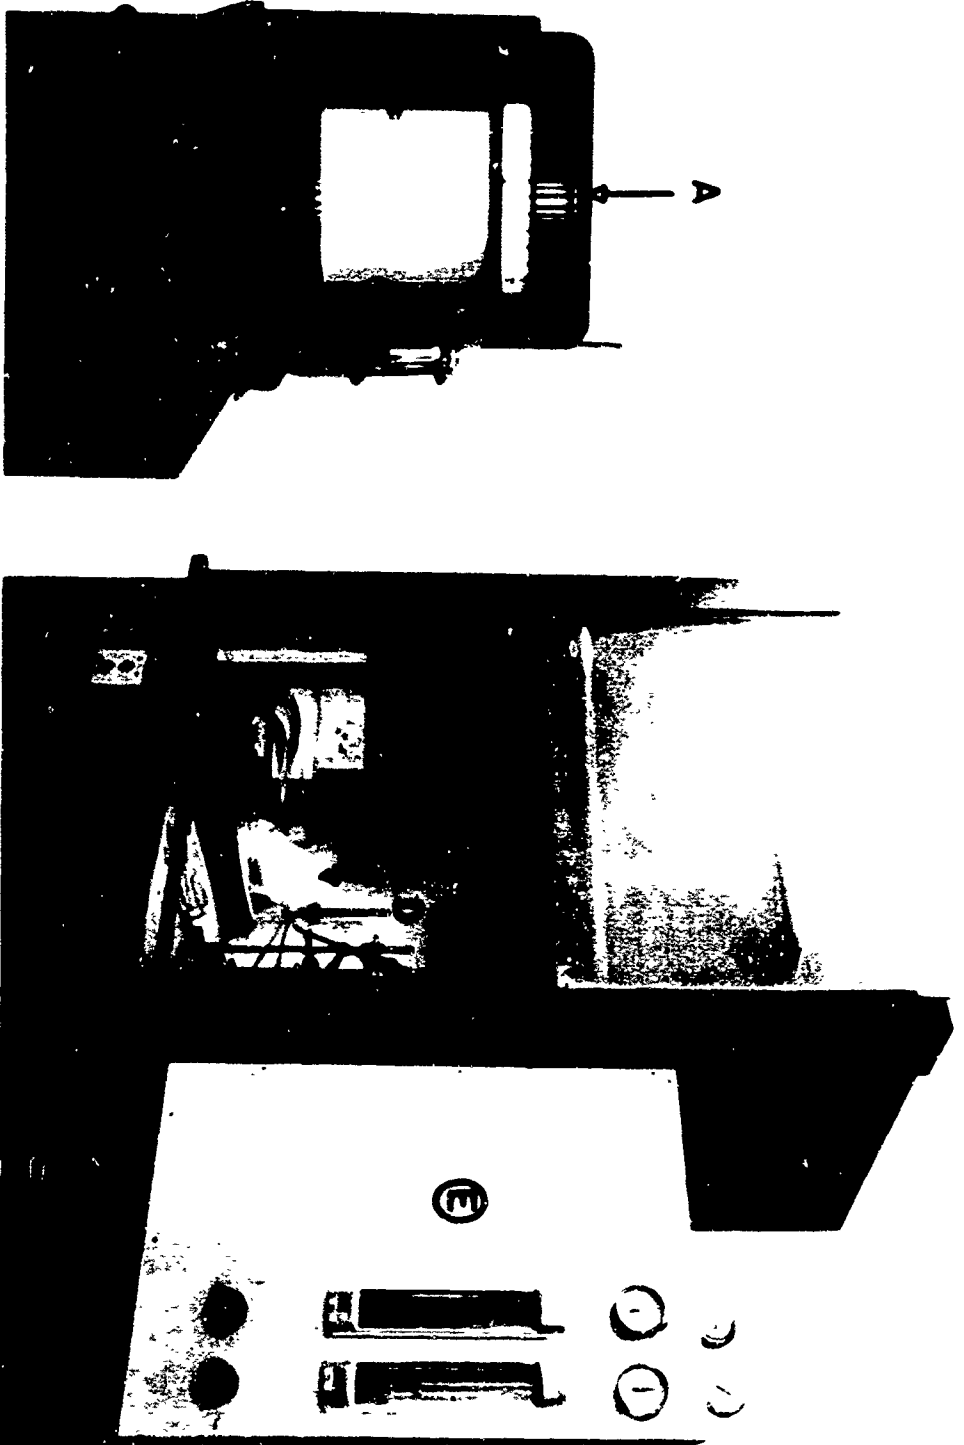

RIA OXY-ACETYLENE TORCH TEST FACILITY

- A - Fast response temperature recorder
- B - Thermocouple holder
- C - Specimen
- D - Torch
- E - Flowmeters and pressure gauges for oxygen and acetylene

Rock Island Arsenal Laboratory
11-070-3564/Ord-61

TABLE I

TORCH TEST OPERATING CONDITIONS

Oxygen flow rate, standard cubic feet/hour (SCFH)	123
Acetylene flow rate, SCFH	102
Volume ratio oxygen to acetylene	1 2
Impingement angle between flame and specimen, degrees	90
Specimen size, inches	4 X 4 X 1/4
Distance from torch tip to specimen, inches	3/4
Method of determining moment of burn through	Visual


Several materials which exhibited excellent resistance to the torch test were evaluated (see Table VII) in static motor firings conducted by the Atlantic Research Corporation and the Allegheny Ballistics Laboratory at their respective test facilities.

The major compounding ingredients for each material tested may be found in the tables pertaining to the material. Curing systems are given in Appendix I. Test specimens were compression molded in a four cavity mold. The liquid polymer-based compounds were mixed in a two bladed sigma type mixer (Figure 2), with mixing arms operating at differential speeds. All solid polymer-based compounds were mixed on a two roll rubber mill. Stress-strain properties were determined in accordance with applicable ASTM(10) procedures

RESULTS AND DISCUSSION

Previous evaluation(9) of several types of inorganic and organic fibers had shown that asbestos was the most effective for imparting thermal resistance to rubber vulcanizates. Current studies were made to determine the effect of the type of asbestos on the properties of insulation materials. Amosite, crocidolite and chrysotile asbestos of approximately equal fiber length (major concentration of fiber lengths, 3/4 to 1 inch long) were evaluated in a nitrile rubber-phenolic resin based compound. Chrysotile samples from three different suppliers were included. The results in Table II show that the three chrysotile-based vulcanizates differ from one another considerably, but that all three are superior to either the amosite or crocidolite-based insulations. The superiority of chrysotile is attributed to its flexibility (both amosite and crocidolite are brittle and tend to suffer fiber breakdown during compounding), higher specific heat and fusion temperature, lower density and higher percent of bound water. Hereinafter, the word "Asbestos"

FIGURE 2

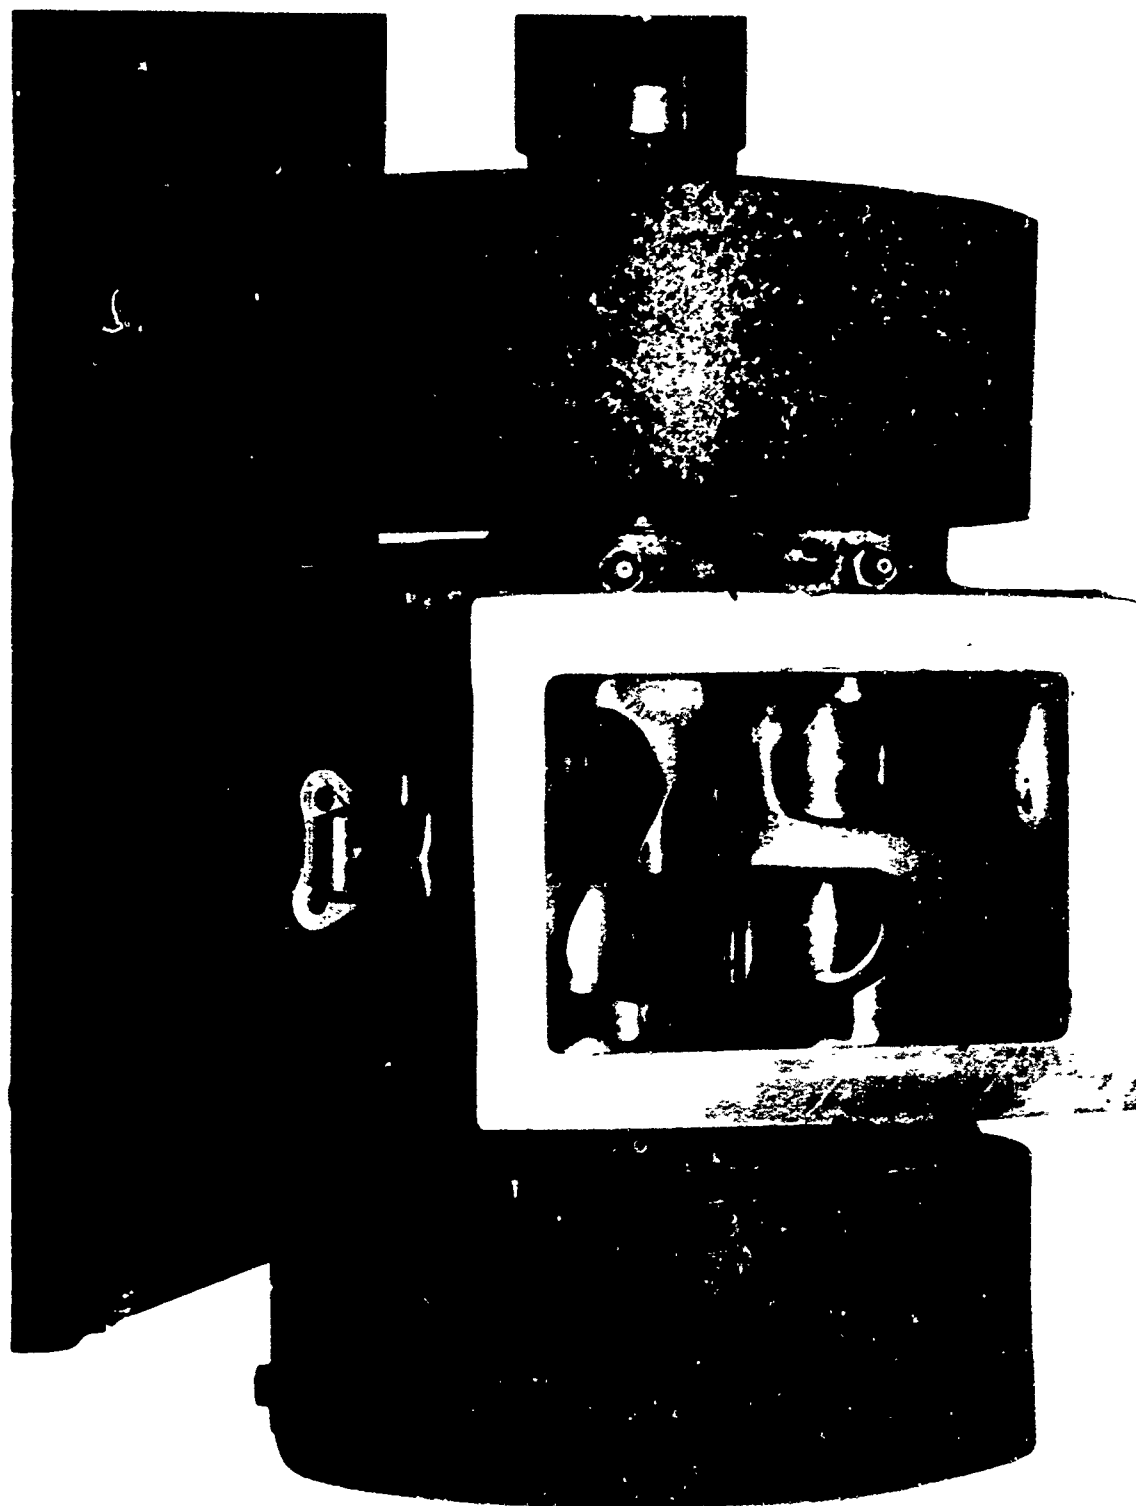

ONE PINT SIGMA MIXER

TABLE II
THE EFFECT OF ASBESTOS TYPE ON PROPERTIES OF INSULATION MATERIALS

Asbestos Type	Asbestos Properties*				Insulation Properties		
	Specific Heat, Cal/gm/°C.	Fusion Temp., °C.	Density, gm/cc	Bound Water, %	P_{200} , cm ² /sec/gm	$\frac{E}{\text{Mils/sec}}$	Elongation, %
Chrysotile #1	0.265	1520	2.4-2.6	13	71	2.8	20
Chrysotile #2	0.266	1520	2.4-2.6	13	58	4.7	25
Chrysotile #3	0.266	1520	2.4-2.6	13	51	4.3	35
Crocidolite	0.201	1190	3.2-3.3	2	29	8.7	105
Amosite	0.193	1400	3.1-3.3	1-5	24	9.6	145

Basic Formulation:

55/45 Butadiene Acrylonitrile 100
 Curatives 9.32
 Phenol Formal Resin, powder 50
 Asbestos 100

*Manufacturer's data.

61

in this report refers to chrysotile #1.

The problem of obtaining a uniform dispersion of long asbestos fibers in a rubber matrix while at the same time minimizing the reduction in fiber length was attacked through the use of the following classes of materials: (1) wetting agents, to wet the asbestos fiber and thus facilitate fiber dispersion; (2) plasticizers, to soften the rubber matrix; (3) liquid polymers, to reduce shearing forces which prevail when solid polymers are mixed; (4) solvents, to dissolve the unvulcanized rubber prior to the asbestos addition.

Evaluations of wetting agents were made as shown in Table III. The wetting agents were added to the mixture just prior to the asbestos. Although most of the wetting agents tested were useful in dispersing the asbestos, not all improved insulation properties. However, oxyazoline #1, a heterocyclic cationic wetting agent, produced vulcanizates with excellent thermal properties. A compound containing 30 PHR of this wetting agent produced a 25 percent improvement in thermal properties and a 100 percent increase in elongation over the control material containing no wetting agent.

Oxyazoline #1 at 30 PHR concentration showed no evidence of migration after aging for 7 days in an air oven at 70°C. Aged specimens when evaluated in the oxyacetylene torch test, exhibited thermal properties equivalent to unaged controls. Insulation containing oxyazoline #1 has been bonded to both aluminum and steel using a two part, room temperature curing, general purpose epoxy adhesive. Bond strengths (tensile shear on one inch lap joints) greater than the tensile strength (1730 psi) of the insulation were achieved.

Data for plasticized solid elastomer-resin-asbestos compounds and unplasticized control compounds are presented in Table IV. Small amounts (5 and 15 PHR) of phosphate esters served to increase elongation but larger amounts decreased elongation. None of the vulcanizates had improved thermal properties over the controls.

Liquid ingredients offer a means of compounding with low shear forces. Data for liquid elastomer-asbestos vulcanizates, as well as the appropriate controls based on solid polymers, are given in Table V. The data revealed the following results: vulcanizates based on liquid elastomers have better thermal properties, greater tensile strength but shorter ultimate elongation than the controls based on solid polymers. The liquid elastomers consisted of low molecular weight, short chain molecules which required

Wetting agent or plasticizer
Average of 8 tests
As Noted

TABLE III
THE EFFECT OF WETTING AGENTS ON PHYSICAL PROPERTIES AND
TORCH PERFORMANCE OF NBR* VULCANIZATES

Wetting agent or plasticizer, PHR	Elongation, %	Tensile, psi	Density, gm/cc	P ₂₀₀ , cm ² /sec/gm	E', mls/sec
Control none	20	2530	1.42	74	2.6
Tri-octyl phosphate Oxyazoline #1	7.5 } 15	3330	1.40	76	2.3
Oxyazoline #1	10	2990	1.39	78	2.2
Oxyazoline #1	20	1460	1.35	87	2.3
Oxyazoline #1	30	1730	1.34	95**	2.0**
Oxyazoline #2	30	1270	1.37	92	2.4
Polyoxyethylene sorbitan monooleate	30	720	1.34	82	2.7
Sorbitan Monooleate	30	710	1.35	75	2.6
Trioctyl phosphate	30	2990	1.37	73	2.5
Tricresyl phosphate	45	1290	1.35	71	2.8
Naphthenic type oil	30	960	1.33	63	3.1

* Basic Formulation:

55/45 Butadiene/acrylonitrile	100
Phenol furfural resin	50
Asbestos	100
Curatives	10
Wetting agent or plasticizer	As Noted

TABLE IV
THE EFFECT OF PLASTICIZERS ON TORCH PERFORMANCE
AND PHYSICAL PROPERTIES OF NBR* VULCANIZATES

Plasticizer, PHR	Resin,** PHR	Asbestos, PHR	P200, cm ² /sec/gm	E, mls/sec	Tensile, psi	Elongation, %	
Control	0	100	50	71	2.8	2600	20
Tri-octyl phosphate	5	100	50	60	3.4	2180	30
Tri-octyl phosphate	15	100	50	71	3.0	1250	45
Tri-cresyl phosphate	5	100	50	60	3.1	2100	30
Tri-cresyl phosphate	15	100	50	65	3.3	2190	50
Control	0	50	100	74	2.6	2530	20
Tri-octyl phosphate	5	50	100	69	2.8	2660	30
Tri-octyl phosphate	15	50	100	69	2.8	1810	40
Tri-octyl phosphate	30	50	100	73***	2.5***	2990	20
Tri-cresyl phosphate	5	50	100	63	3.1	3060	30
Tri-cresyl phosphate	15	50	100	56	3.1	2050	50
Tri-cresyl phosphate	45	50	100	71	2.8	1290	10
Tri-cresyl phosphate Tri-octyl phosphate	7.5 } 7.5 }	50	100	57	3.4	2600	15
Butadiene/acrylonitrile, liquid	15	50	100	56	3.4	3090	35
Control	0	100	100	76	2.3	2830	10
Butadiene/acrylonitrile, liquid	20	100	100	74	3.6	2020	15

* 55/45 Butadiene/acrylonitrile

** Phenol fufural, powder

*** Average of 8 samples

TABLE V
PROPERTIES OF VULCANIZATES BASED ON LIQUID POLYMERS

Elastomer Type	Asbestos, PHR	P200, cm ² /sec/gm.	E, Mils/sec.	Elongation, %	Tensile, psi
76.5/23.5 Butadiene/styrene, solid	100	51	4.7	55	1050
Butadiene/styrene, high viscosity liquid	100	63	3.0	20	2180
55/45 Butadiene/acrylonitrile, solid	100	36	7.2	75	2330
Butadiene/acrylonitrile, liquid	100	47	4.2	20	3600
Carboxy terminated butadiene/ acrylonitrile, liquid	50	57	5.3	15	210
Carboxy terminated butadiene, liquid	50	48	6.1	15	520

a high state of cure to produce good thermal resistance. Although these elastomers did facilitate the incorporation of fibrous asbestos without appreciable fiber breakdown, the high degree of crosslinking required for proper vulcanization produced lower elongations than are inherent with solid polymers.

Further evaluation of liquid elastomers included the addition of thermosetting resins (liquid and solid) as fillers. The resins used in this study were all polar and enhanced the erosion resistance of NBR-based compounds, but they were too incompatible with the less-polar SBR to be effective. Because of the lack of non-polar resins and the low elongations obtained with the liquid elastomers, work with SBR and NBR liquid elastomers was discontinued.

The two carboxy modified polymers listed in Table V were vulcanized using an epoxy resin at a concentration of 13 PHR as a curative. The low elongations obtained from these two compounds eliminated the need for investigating the effect of adding more resin.

The method of incorporating asbestos by adding it to a methyl ethyl ketone solution of the polymer and other compounding ingredients proved unsuccessful. The asbestos in the resultant vulcanizates was non-uniformly dispersed in the rubber matrix after air and vacuum evaporation of the solvent. These vulcanizates had properties inferior to the properties of vulcanizates prepared by conventional milling procedures.

Torch test data for several commercial insulation materials tested are presented in Appendix II. Of these materials, one has properties comparable to the best Rock Island Arsenal insulation, as shown in Table VI.

The work discussed herein and work previously reported^(8,9) has resulted in several excellent thermal insulation materials. The nine best of these, along with five poorer materials and two commercial products, were evaluated in static motor firings by Atlantic Research Corporation. Erosion rates, densities, elongations and major constituents for each are presented in Table VII. The erosion rates from the static firing tests correlate reasonably well with the torch test erosion rates, at least for the best five or six and the poorest compounds. The erosion rates from the static tests cover a range of only 2.4 units, as compared to 10.4 units for the torch test.

Unfortunately the insulation containing oxyazoline #1 wetting agent was not included with the above materials.

TABLE VI
EVALUATION DATA FOR THE BEST ROCK ISLAND ARSENAL
AND COMMERCIAL INSULATIONS

<u>Property Measured</u>	<u>Rock Island Arsenal</u>	<u>Commercial #1</u>
P ₂₀₀ . Cm ² sec/gm	95	79
Time to backside temperature of 200°C. for 1/4" specimen, sec.	127	101
E, mils/sec	2.0	2.0
Elongation, %	40	50
Density, gm/cc	1.34	1.28
Major constituents	Rubber, Resin, Asbestos, Oxyazoline #1	Rubber, Resin, Asbestos

However, this material was submitted to Allegheny Ballistics Laboratory for evaluation in their test facilities. Their data indicates that it compares favorably with materials they class as "current better materials." (11)

COMPARISON OF EROSION RATES FROM OXYACETYLENE TESTS WITH EROSION RATES FROM MOTOR FIRINGS*

TABLE VII

Erosion Rate, Mils/sec. Hock Island Arsenal Torch Test	Static Solid Propellant Motor, Convergent Area		Density, gm/cc		Elongation, %		Major Constituents
2.3	1.5	1.42	10				55/45 Butadiene/acrylonitrile (100), phenol furfural Resin Powder (100), Asbestos (100).
2.5	1.6	1.37	20				55/45 Butadiene/acrylonitrile (100), phenol furfural Resin Powder (50), tri-octyl phosphate (30), asbestos (100).
2.8	1.6	1.41	20				55/45 Butadiene/acrylonitrile (100), phenol furfural resin powder (50), asbestos (100).
3.1	2.2	1.30	20				55/45 Butadiene/acrylonitrile (100), phenol furfural resin powder (100), asbestos (50).
3.1	2.3	1.36	95				Butadiene/acrylonitrile-polyvinyl chloride blend (100), hydrated silica (20), asbestos (40).
3.2	2.5	1.31	30				Butadiene/styrene, high viscosity liquid (100), asbestos (50).
3.2	3.1	1.12	3				Butadiene/acrylonitrile, resin, metal organic salt. Commercial material #3.
3.4	2.6	1.28	25				Butadiene/styrene, low viscosity liquid (100), asbestos (50).
3.5	4.1	1.36	25				Butadiene/styrene, high viscosity liquid (100), hydrated silica (40), asbestos (40).
3.9	2.5	1.34	40				Butadiene/acrylonitrile liquid (100), asbestos (50).
4.1	2.7	1.39	120				Butadiene/styrene, asbestos, commercial material #8.
4.7	2.5	1.26	135				76.5/23.5 Butadiene/styrene (100), hydrated silica (20), asbestos (40).
5.0	2.5	1.33	20				76.5/23.5 Butadiene/styrene (100), phenol furfural resin powder (100), asbestos (50).
5.4	2.5	1.43	65				76.5/23.5 Butadiene/styrene (100), metal oxide mixture (100), asbestos (50).
9.9	3.1	1.55	15				Methyl phenyl vinyl silicone (100), mineral filled silicone resin (50), asbestos (50).
12.7	3.9	1.72	85				Vinylidene fluoride (hexafluoropropylene (100), Polychloroprene (50), metal organic salt (40), MT carbon black (50).

* Pressure, temperature and times of test are classified information.

** Metal oxide mixture composition.

Metal oxide		% Composition	
Al ₂ O ₃	70.0		
Hg O	0.5		
Hydrated silica	26.0		
Fe ₂ O ₃	0.5		
Ca O	0.5		
Ti O ₂	2.5		
	100.0		

LITERATURE REFERENCES

1. Batchelor, J. D. and Vasileff, N., "Solid Propellant Rocket Motor Insulation," Conference on Behavior of Plastics in Advanced Flight Vehicle Environments, WADD Technical Report 60-101, September 1960.
2. Dervy, A. J., "Reinforced Plastics of High Strength/Weight Ratio for Space Applications," Society of the Plastics Industry, Inc., 17th Annual Technical and Management Conference, Reinforced Plastics Division, Chicago, Illinois; 6,7,8 February 1962.
3. Epstein, G., Cecka, A. M. and Robbins, D. L., "Plastics in Rocket Nozzle Environments," Conference on Behavior of Plastics in Advanced Flight Vehicle Environments, WADD Technical Report 60-101, September 1960.
4. Epstein, G. and Jaffe, E. H., "Materials for Internal Thermal Protection of Rocket Motor Cases. A State-of-the Art Survey," Society of the Plastics Industry, Inc., 17th Annual Technical and Management Conference, Reinforced Plastics Division, Chicago, Ill; 6,7,8 February 1962.
5. Hazelrigg, W. K., "Design Criteria for Insulation Materials " a paper presented to the Refractory Material Working Group, Aerojet-General Corporation, Sacramento, California, 14 July 1960.
6. Headrick, R. E., "Ablative Elastomeric Insulation Materials," Directorate of Materials and Processes, Wright-Patterson Air Force Base, ASD-TDR-62-400, August 1962.
7. Sewell, J. J. and Kuno, J. K., "Aerospace Use of Plastic Hardware and Thermal Insulation," Society of the Plastics Industry, Inc., 17th Annual Technical and Management Conference, Reinforced Plastics Division, Chicago, Illinois; 6,7,8 February 1962.
8. Rock Island Arsenal Laboratory Report No. 61-2315, 2 August 1961. "Evaluation of Flexible Insulation for Solid Propellant Rocket Motor Cases."
9. Rock Island Arsenal Laboratory Report No. 62-2366, 6 July 1962, "Development of Flexible Insulation for Solid Propellant Rocket Motor Cases."

10. American Society for Testing Materials, October 1961.
"ASTM Standards on Rubber Products," 1916 Race Street,
Philadelphia, Pa.
11. Confidential Communication, Allegheny Ballistics
Laboratory to Rock Island Arsenal, Subject:
"Evaluation of Candidate Insulation Material"(U),
25 June 1964.

APPENDIX I

CURRY, SYSTHIA

PIIK Used for Compounds Based On

Ingredients	Solid NBR containing resin fillers	Solid NBR without resin fillers	Liquid CB-foam terminated polymers	Solid SBR	Liquid SBR	Acrylic phenyl vinyl siloxane	Vinylidene Fluoride
							Optical spectroscopy
							blended with polyisobutylene

Ingredients

Stearic acid

2100 0017

Tolson

Swissair

Benzothiazyl disulfide

Activated dithiocarbamate

2, 4, 6

ÉΡΟΥ

N-phenyl-1-beta-naphthylamine

Zinc diethylidithiocarbamate

2,4-dichlorobenzoyl peroxide with

MARKED FOR DESTRUCTION

SECRET

Circlag cycle for .035" thick specimens

Press Time, minutes/temperature, °C

Alf oven cont cure	Time hour temp.
50C	

15

2

15

14

APPENDIX II

TORCH TEST DATA FOR COMMERCIAL INSULATION MATERIALS

Material #	P_{200} , cm ² /sec/cm	E , mils/sec	Density, gm/cc	Elongation, %	Major Constituents
1	79	2.0	1.26	50	Rubber - Resin - Asbestos
2	79	2.1	1.65	nil	Resin - Asbestos - Polyamide
3	72	3.2	1.12	3	NBR Rubber - Resin - Methal organic salt
4*	69	3.0	1.45	10	Rubber - Resin - Asbestos
5	63	3.5	1.25	50	Rubber - Resin - Asbestos
6	46	2.1	1.24	30	NBR Rubber - Resin - Carbon fibers
7*	46	5.6	1.23	90	Rubber - Resin - Asbestos
8	45	4.0	1.32	120	SBR Rubber - . . . - Asbestos
9	35	6.9	1.29	25-225	NBR Rubber - . . . - Asbestos
10	30	13.2	0.60	100	Silicone Rubber - . . . - Inorganic fillers
11	27	5.5	1.77	nil	Resin - Asbestos

* Data is average of 2 specimens

DISTRIBUTION

No. of Copies

A. Department of Defense

Office of the Director of Defense
Research & Engineering
ATTN: Mr. J. C. Barrett
Room 3D-1005, The Pentagon
Washington 25, D. C.

1

Commander
Defense Documentation Center
ATTN: TDDR
Cameron Station
Alexandria, Virginia 22314

20

B. Department of the Army - Technical Services

Commanding General
U.S. Army Materiel Command
Room 2502, Bldg. T-7
ATTN: AMCRD-RS-CM
Washington, D. C. 20315

1

Commanding Officer
U.S. Army Coating and Chemical Laboratory
ATTN: Dr. C. Pickett
Technical Library
Aberdeen Proving Ground, Maryland 21005

1

1

Commanding General
U.S. Army Tank Automotive Center
ATTN: SMOTA-REM.2
SMOTA-REM.3
Warren, Michigan 48090

1

1

Commanding General
U.S. Army Weapons Command
ATTN: AMSWE-RD
AMSWE-PP
Rock Island Arsenal
Rock Island, Illinois

1

1

DISTRIBUTION

	<u>No. of Copies</u>
Commanding General U.S. Army Missile Command ATTN: Documentation & Technical Information Branch	2
Mr. R. E. Ely, AMSMI-RRS	1
Mr. R. Fink, AMSMI-RKX	1
Mr. W. K. Thomas, AMSMI	1
Mr. E. J. Wheelahan, AMSMI-RSM	1
Redstone Arsenal, Alabama 35809	
 Commanding Officer Frankford Arsenal ATTN: SMUFA-1330	1
Library-0270	1
Philadelphia, Pa. 19137	
 Commanding Officer U.S. Army Materials Research Agency Watertown Arsenal ATTN: RPD	
Watertown, Mass. 02170	1
 Commanding Officer Picatinny Arsenal ATTN: Plastics & Packaging Lab.	1
PLASTECH	1
Dover, New Jersey 07801	
 Commanding Officer Springfield Armory ATTN: SWESP-TX	
Springfield, Mass. 01101	1
 Commanding Officer Watertown Arsenal ATTN: SMIWT-LX	
Watertown, Mass. 02170	1
 Commanding Officer Watervliet Arsenal ATTN: SWEWV-RDR	
Watervliet, New York 12189	1
 Commanding General U.S. Army Munitions Command Dover, New Jersey 07801	1

DISTRIBUTION

	<u>No. of Copies</u>
Commanding Officer U.S. Army Environmental Health Laboratory Army Chemical Center, Maryland	1
Commanding Officer U.S. Army Chemical Warfare Laboratories ATTN: Technical Library Army Chemical Center, Maryland	1
Commanding Officer Harry Diamond Laboratory ATTN: Technical Library Washington, D, C. 20438	1
Commanding Officer U.S. Army Engineer R&D Laboratories ATTN: Chemistry Research Section, Materials Branch Fort Belvoir, Virginia	1
Commanding Officer U.S. Army Electronics R&D Laboratories ATTN: Mr. Dan Lichtenstein-PEE Materials Branch Fort Monmouth, New Jersey 07703	1 1
Commanding General Quartermaster R&D Command ATTN: Clothing & Organic Materials Div. Natick, Massachusetts 01762	1
Commanding Officer U.S. Army Prosthetics Research Laboratory Forest Glen, Maryland	1
<u>Department of the Army - Other Army Agencies</u>	
U.S. Army Reactor Branch Division of Reactor Development Atomic Energy Commission Washington 25, D. C.	1
Commander U.S. Army Research Office Arlington Hall Station Arlington 12, Virginia	1

DISTRIBUTION

No. of Copies

Commanding Officer
U.S. Army Research Office (Durham)
Box CM, Duke Station
Durham, North Carolina 1

Chief of Research & Development
U.S. Army Research & Development
Liaison Group
ATTN: Dr. B. Stein
APO 757
New York, N. Y. 1

Commanding Officer
U.S. Army Aviation School
ATTN: Office of the Librarian
Fort Rucker, Alabama 1

C. Department of the Navy

Chief
Bureau of Naval Weapons
Department of the Navy
ATTN: RMMP
Room 2225, Munitions Building
Washington 25, D. C. 1

Commander
Department of the Navy
Office of Naval Research
ATTN: Code 423
Washington 25, D. C. 1

Chief
Department of the Navy
Bureau of Ships
ATTN: Code 344
Washington 25, D. C. 1

Commander
Department of the Navy
Special Projects Office
ATTN: SP 271
Washington 25, D. C. 1

Commander
U.S. Naval Ordnance Laboratory
ATTN: Code WM
White Oak, Silver Spring, Maryland 1

DISTRIBUTION

No. of Copies

Commander U.S. Naval Ordnance Test Station ATTN: Technical Library Branch China Lake, California	1
Commander U.S. Naval Research Laboratory ATTN: Technical Information Center Anacostia Station Washington 25, D. C.	1
Commander Mare Island Naval Shipyard ATTN: Rubber Laboratory Vallejo, California	1
 D. <u>Department of the Air Force</u>	
U. S. Air Force Directorate of Research and Development ATTN: Lt. Col. J. B. Shipp, Jr. Room 4D-313, The Pentagon Washington 25, D. C.	1
Commander Wright Air Development Division ATTN: ASRCEE-1 WWRCO Materials Central Wright-Patterson Air Force Base, Ohio	1 1 1
6593 Test Group (Development) ATTN: Solid Systems Division, DGSC Edwards Air Force Base, California	1
Commander AMC Aeronautical Systems Center ATTN: Manufacturing & Materials Technology Division, LMBMO Wright-Patterson Air Force Base, Ohio	2
Commanding Officer Brookley Air Force Base ATTN: Air Force Packaging Laboratory Alabama	1

DISTRIBUTION

No. of Copies

E. Other Government Agencies

Scientific & Technical Information Facility	
ATTN: NASA Representative (SAK/DL)	1
Mr. B. G. Achhammer	1
Mr. G. C. Deutsch	1
Mr. R. V. Rhode	1
P.O. Box 5700	
Bethesda, Maryland 20014	
 George C. Marshall Space Flight	
ATTN: M-S&M-M	1
M-R&AE-M	1
Huntsville, Alabama 35800	
 Commanding General	
U.S. Army Weapons Command	
ATTN: AMSWE-RD	3
Rock Island Arsenal	
Rock Island, Illinois	
for	
release to	
 Commander	
British Army Staff	
ATTN: Reports Officer	
3100 Massachusetts Avenue, N. W.	
Washington 8, D. C.	
 Commanding General	
U.S. Army Weapons Command	
ATTN: AMSWE-RD	3
Rock Island Arsenal	
Rock Island, Illinois	
for	
release to	
 Canadian Army Staff, Washington	
ATTN: GSO-1, A&R Section	
2450 Massachusetts Avenue, N. W.	
Washington 8, D. C.	
 Prevention of Deterioration Center	
National Academy of Science	
National Research Council	
2101 Constitution Avenue	
Washington 25, D. C.	1

DISTRIBUTION

No. of Copies

Chief, Input Section
Clearinghouse for Federal Scientific
and Technical Information, CFSTI
Sills Building
5285 Port Royal Road
Springfield, Virginia 22151

30

Accession No. _____
Rock Island Arsenal Laboratory, Rock Island, Illinois

UNCLASSIFIED

ELASTOMERIC INSULATION FOR SOLID PROPELLANT ROCKET MOTORS. By D. H. Sale

RIA Lab. Rep. 64-3158, 27 Oct 64, 24 p. Incl. 111us, tables. (DA Project No. 1CO-24401-A110, AWC Code No. 5025.11.84203) Unclassified Report

The development of flexible, elastomeric-based, solid propellant rocket motor case insulation is discussed. The effect on insulation properties of type of asbestos, of liquid versus solid elastomers and of methods of dispersing fibrous compounding ingredients, are reported. Oxycetylene torch and static motor firing test data for some of the better insulation materials developed, as well as for some commercial materials, are presented. The torch test, the principle screening tool used in this study, conforms to the test currently being standardized by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20. A material with 40 percent

(Cont) over

1. Insulation - Materials

2. Insulating Compounds - Development

3. Rocket Motors - Materials

DISTRIBUTION:
Copies obtainable from DDC.

Accession No. _____
Rock Island Arsenal Laboratory, Rock Island, Illinois

UNCLASSIFIED

ELASTOMERIC INSULATION FOR SOLID PROPELLANT ROCKET MOTORS. By D. H. Sale

RIA Lab. Rep. 64-3158, 27 Oct 64, 24 p. Incl. 111us, tables. (DA Project No. 1CO-24401-A110, AWC Code No. 5025.11.84203) Unclassified Report

The development of flexible, elastomeric-based, solid propellant rocket motor case insulation is discussed. The effect on insulation properties of type of asbestos, of liquid versus solid elastomers and of methods of dispersing fibrous compounding ingredients, are reported. Oxycetylene torch and static motor firing test data for some of the better insulation materials developed, as well as for some commercial materials, are presented. The torch test, the principle screening tool used in this study, conforms to the test currently being standardized by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20. A material with 40 percent

(Cont) over

1. Insulation - Materials

2. Insulating Compounds - Development

3. Rocket Motors - Materials

DISTRIBUTION:
Copies obtainable from DDC.

Accession No. _____
Rock Island Arsenal Laboratory, Rock Island, Illinois

UNCLASSIFIED

ELASTOMERIC INSULATION FOR SOLID PROPELLANT ROCKET MOTORS. By D. H. Sale

RIA Lab. Rep. 64-3158, 27 Oct 64, 24 p. Incl. 111us, tables. (DA Project No. 1CO-24401-A110, AWC Code No. 5025.11.84203) Unclassified Report

The development of flexible, elastomeric-based, solid propellant rocket motor case insulation is discussed. The effect on insulation properties of type of asbestos, of liquid versus solid elastomers and of methods of dispersing fibrous compounding ingredients, are reported. Oxycetylene torch and static motor firing test data for some of the better insulation materials developed, as well as for some commercial materials, are presented. The torch test, the principle screening tool used in this study, conforms to the test currently being standardized by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20. A material with 40 percent

(Cont) over

1. Insulation - Materials

2. Insulating Compounds - Development

3. Rocket Motors - Materials

DISTRIBUTION:
Copies obtainable from DDC.

Accession No. _____
Rock Island Arsenal Laboratory, Rock Island, Illinois

UNCLASSIFIED

ELASTOMERIC INSULATION FOR SOLID PROPELLANT ROCKET MOTORS. By D. H. Sale

RIA Lab. Rep. 64-3158, 27 Oct 64, 24 p. Incl. 111us, tables. (DA Project No. 1CO-24401-A110, AWC Code No. 5025.11.84203) Unclassified Report

The development of flexible, elastomeric-based, solid propellant rocket motor case insulation is discussed. The effect on insulation properties of type of asbestos, of liquid versus solid elastomers and of methods of dispersing fibrous compounding ingredients, are reported. Oxycetylene torch and static motor firing test data for some of the better insulation materials developed, as well as for some commercial materials, are presented. The torch test, the principle screening tool used in this study, conforms to the test currently being standardized by the Flame Ablation Test Group of Section III-L of ASTM Committee D-20. A material with 40 percent

(Cont) over

1. Insulation - Materials

2. Insulating Compounds - Development

3. Rocket Motors - Materials

DISTRIBUTION:
Copies obtainable from DDC.

elongation, 1.34 gm/cc density, performance index of 95 cm²/sec/cm and erosion rate of 2.0 mils/sec was the most promising insulation developed. The material is a 55/45 butadiene/acrylonitrile compound containing phenol furfural resin, asbestos and oxazoline wetting agent. It has been satisfactorily bonded to aluminum and to steel by conventional bonding agent. The thermal properties of this vulcanizate are not affected by oven aging for one week at 700°C.

elongation, 1.34 gm/cc density, performance index of 95 cm²/sec/cm and erosion rate of 2.0 mils/sec was the most promising insulation developed. The material is a 55/45 butadiene/acrylonitrile compound containing phenol furfural resin, asbestos and oxazoline wetting agent. It has been satisfactorily bonded to aluminum and to steel by conventional bonding agent. The thermal properties of this vulcanizate are not affected by oven aging for one week at 700°C.

elongation, 1.34 gm/cc density, performance index of 95 cm²/sec/cm and erosion rate of 2.0 mils/sec was the most promising insulation developed. The material is a 55/45 butadiene/acrylonitrile compound containing phenol furfural resin, asbestos and oxazoline wetting agent. It has been satisfactorily bonded to aluminum and to steel by conventional bonding agent. The thermal properties of this vulcanizate are not affected by oven aging for one week at 700°C.

elongation, 1.34 gm/cc density, performance index of 95 cm²/sec/cm and erosion rate of 2.0 mils/sec was the most promising insulation developed. The material is a 55/45 butadiene/acrylonitrile compound containing phenol furfural resin, asbestos and oxazoline wetting agent. It has been satisfactorily bonded to aluminum and to steel by conventional bonding agent. The thermal properties of this vulcanizate are not affected by oven aging for one week at 700°C.